



# Phase, Microstructure and Dielectric Properties of Sodium Bismuth Titanate Based Ceramics

Afzal Shah<sup>1</sup>, Shakeela Naz<sup>1</sup>, Shah Faisal<sup>1</sup>, Qaisar Iqbal<sup>2</sup>, Sher Abdullah<sup>2</sup> and Abdul Manan<sup>2,\*</sup>

<sup>1</sup>Department of Chemical Sciences, University of Science & Technology Bannu, Bannu 28100, Pakistan

<sup>2</sup>Laboratory for Research in Advanced Materials, Department of Physics and Materials Science, University of Science & Technology Bannu, Bannu 28100, Pakistan

## Abstract

In this study, ceramics in the  $0.90\text{Na}_{0.5}\text{Bi}_{0.5-x}\text{La}_x\text{TiO}_3-0.03\text{NaNbO}_3-0.07\text{Ba}(\text{Zr}_{0.2}\text{Ti}_{0.8})\text{O}_3$  series (where  $x = 0.00, 0.03, 0.05, 0.07$ ) were processed via a solid-state reaction method. The phase, microstructural features, and dielectric properties, particularly the dielectric constant and dielectric loss, were studied using X-ray diffraction (XRD), scanning electron microscopy (SEM), and dielectric spectroscopic techniques, respectively. XRD analysis revealed a single perovskite phase, while SEM analysis showed a dense microstructure with reduced grain size as the  $x$  content increased. The increase in doping content enhanced the relaxor characteristics, which consequently reduced the dielectric loss to below 0.05 for  $x = 0.07$ .

**Keywords:** solid-state reactions, relaxor behavior, dielectric characteristics.

## 1 Introduction

The field of ferroelectric materials has attracted significant attention due to their unique dielectric properties that could be useful in electronic technology [1, 2]. Ferroelectrics, when converted to a relaxor state, displayed a high piezoelectric response when subjected to an external electric field or mechanical pressure. Relaxor ferroelectrics with polar nano-regions (PNRs) are also useful in electrostatic capacitors for electrical energy storage [3, 4]. Lead-free ceramic systems optimized for energy storage, including modified titanate-based compositions, have demonstrated that relaxor behavior is a key design parameter for achieving high capacitive energy density [5]. Lead-based (Pb) materials have proven to possess the above characteristics, but growing concern over the environmental and health hazards of Pb has driven the search for lead-free alternatives [6, 7]. The focus has been changed on the fabrication of dielectric materials with lead alternatives. In this perspective,  $\text{Na}_{0.5}\text{Bi}_{0.5}\text{TiO}_3$  (BNT)-based ceramics attracted great attention because of their good piezoelectric performance [8]. BNT ceramics were first reported by Isupov et al. [9], with a high Curie temperature ( $T_c$ ) of  $\sim 320^\circ\text{C}$  and possess normal ferroelectric nature. In its pure form,



Submitted: 29 May 2026

Accepted: 17 June 2026

Published: 29 June 2026

Vol. 2, No. 2, 2026.

doi:10.62762/JAEM.2026.298040

\*Corresponding author:

✉ Abdul Manan

drmanan82@ustb.edu.pk, drmanan82@yahoo.com

## Citation

Shah, A., Naz, S., Faisal, S., Iqbal, Q., Abdullah, S., & Manan, A. (2026). Phase, Microstructure and Dielectric Properties of Sodium Bismuth Titanate Based Ceramics. *Journal of Advanced Electronic Materials*, 2(2), 64–68.




© 2026 by the Authors. Published by Institute of Central Computation and Knowledge. This is an open access article under the CC BY license (<https://creativecommons.org/licenses/by/4.0/>).

BNT exhibits high remanent polarization, making it one of the most promising lead-free alternatives; early fundamental work on BNT with diffuse phase transitions established the basis for understanding its ferroelectric behavior [10]. However, in its pure form, BNT exhibits various problems, such as high electric conductivity, large remnant polarization requiring a high coercive field, and consequently giving problems in the poling process [11], which avoids its practical applications.

Many studies have demonstrated improvement in the properties by doping suitable cations at the A/B site of its perovskite structure or by incorporation with other components to form solid solutions [12, 13].

In recent years, research in BNT-based ceramics has focused on two features. One aspect is the phase transformation and structural change under external stimuli such as electric fields, temperature, and stress fields. The other aspect of research is the enhancement of properties of BNT-based by doping or by making solid solutions with other end members, such as  $\text{Bi}_{0.5}\text{Na}_{0.5}\text{TiO}_3$ - $\text{BaTiO}_3$  [14],  $\text{Bi}_{0.5}\text{Na}_{0.5}\text{TiO}_3$ - $\text{Bi}_{0.5}\text{K}_{0.5}\text{TiO}_3$  (BNT-BKT) [15], and several other systems.

The present study focused on the investigation of phase, microstructure and dielectric properties of  $0.9\text{Na}_{0.5}\text{Bi}_{0.5-x}\text{La}_x\text{TiO}_3 - 0.07\text{Ba}(\text{Zr}_{0.2}\text{Ti}_{0.8})\text{O}_3 - 0.03\text{NaNbO}_3$  ( $x = 0.00, 0.03, 0.05, 0.07$ ) system processed via solid state sintering method.

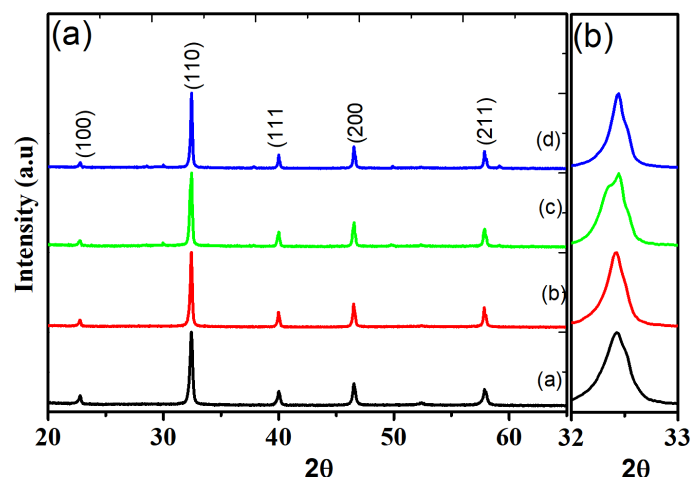

**Figure 1.** XRD spectrum of  $0.9\text{Na}_{0.5}\text{Bi}_{0.5-x}\text{La}_x\text{TiO}_3 - 0.07\text{Ba}(\text{Zr}_{0.2}\text{Ti}_{0.8})\text{O}_3 - 0.03\text{NaNbO}_3$  ( $x = 0.00, 0.03, 0.05, 0.07$ ) ceramics: (a)  $x = 0.00$ , (b)  $x = 0.03$ , (c)  $x = 0.05$ , (d)  $x = 0.07$ .

## 2 Experimental Procedure

The ceramic compositions in  $0.9\text{Na}_{0.5}\text{Bi}_{0.5-x}\text{La}_x\text{TiO}_3 - 0.07\text{Ba}(\text{Zr}_{0.2}\text{Ti}_{0.8})\text{O}_3 - 0.03\text{NaNbO}_3$  ( $x = 0.00, 0.03,$

$0.05, 0.07$ ) series were fabricated through the utilization of solid state sintering procedure using  $\text{Na}_2\text{CO}_3$ ,  $\text{Bi}_2\text{O}_3$ ,  $\text{BaCO}_3$ ,  $\text{La}_2\text{O}_3$ ,  $\text{TiO}_2$ ,  $\text{ZrO}_2$ ,  $\text{Nb}_2\text{O}_5$ , where purity level  $\geq 99\%$  for each as raw materials that were weighed via an electronic scale in stoichiometric ratios. Following that, these powders were mixed for every batch composition using a specially made 60 mL plastic container, ethanol (purity 99.8%, Sigma Aldrich) as the milling agent, and about 10.7 mm zirconia balls as the grinding medium. The mixture was ball-milled using horizontal ball milling machine for 24 hours to remove agglomerates and produce tiny, homogeneous particles, followed by formation of slurry for each composition. The slurry of each batch was dried in an electric oven at around  $100^\circ\text{C}$ .

For the formation of solid solution, the milled powders of each batch composition was then calcined by heating them at  $850^\circ\text{C}$  at a heating and cooling rate of  $3^\circ\text{C}/\text{min}$  for 2 h while placing in covered alumina crucibles followed by re-milling for 24 hours to make fine powders. Pellets of the powders were made by pressing into 12 mm diameter and a thickness of less than 1 mm under a pressure of  $\sim 100$  MPa followed by sintering in air at  $1150^\circ\text{C}$  for 2 h.


Following the sintering process, the pellet surfaces underwent well polishing, ethanol cleaning, and pasted with conductive silver past on opposite faces to create electrodes followed by heating at  $550^\circ\text{C}$  for 1 h. The edges of silver coated pellets were cleaned to prevent short circuits followed by measuring the dielectric properties such as dielectric constant and dielectric loss in the temperature range of 30 to  $500^\circ\text{C}$  at four different frequencies via LCR meter.

X-ray diffraction (XRD) was used to analyze the crystalline structure and phase purity of the sintered samples of each composition. The microstructure was examined using scanning electron microscopy technique for thermally etched polished surfaces of sintered sample of each composition.


## 3 Results and Discussion

### 3.1 Phase Examination

Figure 1 shows the XRD spectra of fine powders of optimally sintered pellets of  $0.9\text{Na}_{0.5}\text{Bi}_{0.5-x}\text{La}_x\text{TiO}_3 - 0.07\text{Ba}(\text{Zr}_{0.2}\text{Ti}_{0.8})\text{O}_3 - 0.03\text{NaNbO}_3$  ( $x = 0.00, 0.03, 0.05, 0.07$ ). A solid solution without a secondary phase was formed for each ceramic composition, as proven by XRD analysis performed at room temperature with a Panaytical XPert-3 diffractometer. The  $\text{La}^{3+}$  ion ( $1.36 \text{ \AA}$ ) is bigger than  $\text{Bi}^{3+}$  ( $1.31 \text{ \AA}$ ), according to

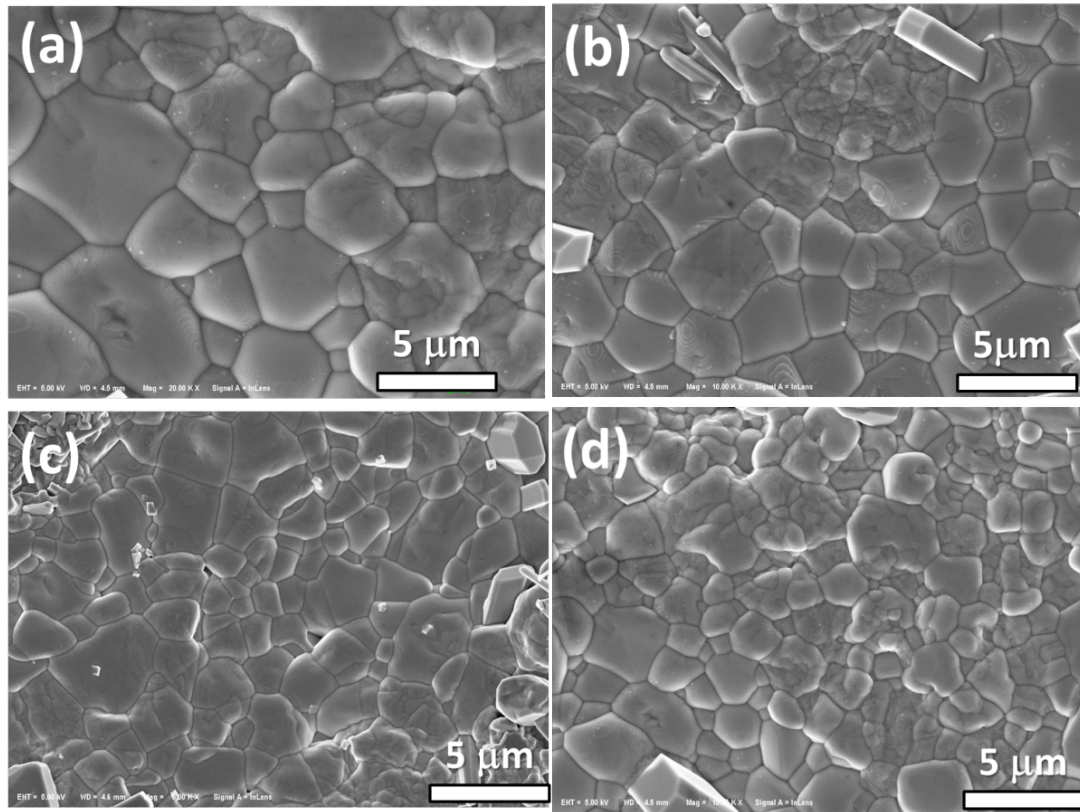

**Figure 2.** SEM images, showing measured grain sizes of  $0.90\text{Na}_{0.5}\text{Bi}_{0.5-x}\text{La}_x\text{TiO}_3-0.07\text{Ba}(\text{Zr}_{0.2}\text{Ti}_{0.8})\text{O}_3-0.03\text{NaNbO}_3$  ( $x = 0.00, 0.03, 0.05, 0.07$ ) ceramics (a)  $x = 0.00$ , (b)  $x = 0.03$ , (c)  $x = 0.05$ , (d)  $x = 0.07$ .

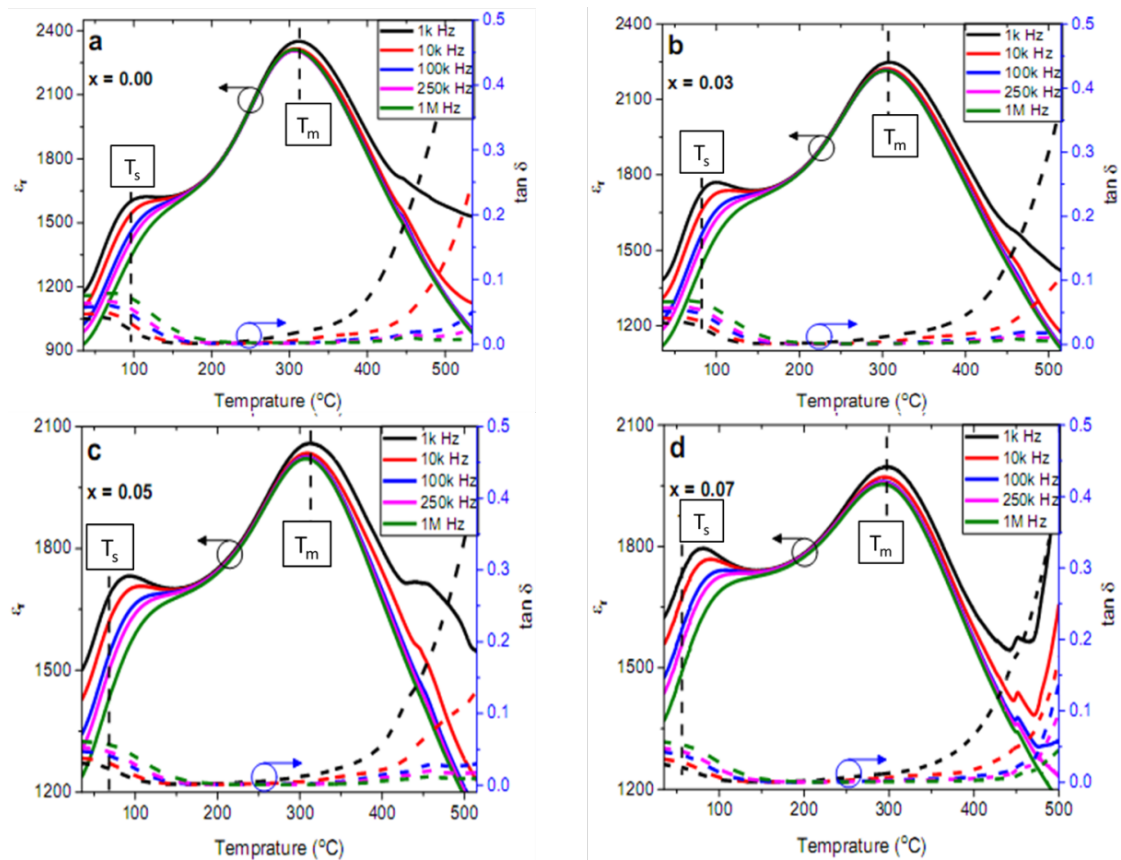

**Figure 3.** Variation of  $\epsilon_r$  and  $\tan \delta$  of  $0.90\text{Na}_{0.5}\text{Bi}_{0.5-x}\text{La}_x\text{TiO}_3-0.07\text{Ba}(\text{Zr}_{0.2}\text{Ti}_{0.8})\text{O}_3-0.03\text{NaNbO}_3$  ( $x = 0.00, 0.03, 0.05, 0.07$ ) ceramics as a function of temperature measured at different frequencies.

Shannon's findings [16]; therefore, its substitution resulted in unit cell expansion, which shifted the XRD peaks to lower  $2\theta$  values as per Bragg's law as shown in the enlarge view of (110) peak in Figure 1(b). The single (200) peak for each composition indicates pseudocubic symmetry [17].

### 3.2 Microstructural Examination

The surface feature in the form of grain distribution of thermally etched surfaces of  $0.90\text{Na}_{0.5}\text{Bi}_{0.5-x}\text{La}_x\text{TiO}_3 - 0.07\text{Ba}(\text{Zr}_{0.2}\text{Ti}_{0.8})\text{O}_3 - 0.03\text{NaNbO}_3$  ( $x = 0.00, 0.03, 0.05, 0.07$ ) ceramics sintered at  $1150^\circ\text{C}$  for 2 h is shown in Figure 2. All ceramics exhibit well-defined grain boundaries and connections, indicating effective densification for each composition. The average grain size is observed to decrease with increasing  $x$  content. The more uniform microstructure in the doped samples is beneficial for enhancing dielectric and electrical properties, particularly in reducing leakage current and enhancing resistivity [18].

### 3.3 Dielectric Properties Determination

The variation of dielectric constant ( $\epsilon_r$ ) as well as the dielectric loss ( $\tan\delta$ ) measured in the temperature range of  $30^\circ\text{C}$  to  $500^\circ\text{C}$  for  $0.90\text{Na}_{0.5}\text{Bi}_{0.5-x}\text{La}_x\text{TiO}_3 - 0.07\text{Ba}(\text{Zr}_{0.2}\text{Ti}_{0.8})\text{O}_3 - 0.03\text{NaNbO}_3$  ( $x = 0.00, 0.03, 0.05, 0.07$ ) ceramics are depicted in Figure 3(a–d).

Two anomalies in the dielectric peaks at different temperatures are observed for each composition. The peak at low temperature labeled as  $T_s$  that describe ferroelectric to relaxor transition, shifted to low temperature as  $x$  increases in accordance with previous research showing strong frequency dispersion. The peak at high temperature where the dielectric constant reaches to its maximum value occur at temperature denoted as  $T_m$  and above which the material attain paraelectric state. The peak at  $T_m$  became broad and slightly suppressed with decreasing  $\epsilon_r$  as the  $x$  content increased from 0.0 to 0.07.

The lower ionic dielectric polarizability of La than Bi caused the decrease in  $\epsilon_r$  with increasing  $x$  content from 0.0 to 0.07. The peak broadening at  $T_m$  is also a sign of increasing relaxor behavior with increasing  $x$  content. The dielectric loss is observed to decrease from  $\sim 0.08$  to  $\sim 0.04$  with increasing  $x$  content from 0.0 to 0.07 measured at 1 kHz at room temperature due to a decreased polarization.

## 4 Conclusion

In this study, traditional solid-state reaction technique was used to successfully synthesize lead-free  $0.90\text{Na}_{0.5}\text{Bi}_{0.5-x}\text{La}_x\text{TiO}_3 - 0.07\text{Ba}(\text{Zr}_{0.2}\text{Ti}_{0.8})\text{O}_3 - 0.03\text{NaNbO}_3$  ( $x = 0.00, 0.03, 0.05, 0.07$ ) ceramics. The development of a single-phase perovskite structure devoid of any discernible secondary phases was validated by XRD investigation. Furthermore,  $\text{La}^{3+}$  doping decreased grain size, resulting in a microstructure that was denser and more compact. An increase in relaxor-like behavior was also facilitated by the presence of  $\text{La}^{3+}$ .

## Data Availability Statement

Data will be made available on request.

## Funding

This work was supported by the Higher Education Commission of Pakistan under Grant LCF-5.

## Conflicts of Interest

The authors declare no conflicts of interest.

## AI Use Statement

The authors declare that no generative AI was used in the preparation of this manuscript.

## Ethical Approval and Consent to Participate

Not applicable.

## References

- [1] Xu, Y. (2013). *Ferroelectric materials and their applications*. Elsevier.
- [2] Zhou, X., Xue, G., Luo, H., Bowen, C. R., & Zhang, D. (2021). Phase structure and properties of sodium bismuth titanate lead-free piezoelectric ceramics. *Progress in Materials Science*, 122, 100836. [CrossRef]
- [3] Bobic, J. D., Petrovic, M. M. V., & Stojanovic, B. D. (2018). Review of the most common relaxor ferroelectrics and their applications. In *Magnetic, ferroelectric, and multiferroic metal oxides* (pp. 233-249). Elsevier. [CrossRef]
- [4] Li, F., Zhang, S., Damjanovic, D., Chen, L. Q., & Shrout, T. R. (2018). Local structural heterogeneity and electromechanical responses of ferroelectrics: learning from relaxor ferroelectrics. *Advanced Functional Materials*, 28(37), 1801504. [CrossRef]
- [5] Rehman, M. U., Manan, A., Uzair, M., Amer, M., Khan, M. A., Ullah, S. W., ... & Shah, H. U. (2023). Enhanced

- energy storage performance of MnO<sub>2</sub>-modified 0.92 BaTiO<sub>3</sub>-0.08 Bi (Mg<sub>0.5</sub>Ce<sub>0.5</sub>) O<sub>3</sub> ceramics for capacitor applications. *ACS Applied Electronic Materials*, 5(8), 4564-4575. [CrossRef]
- [6] Ahn, C. W., Hong, C. H., Choi, B. Y., Kim, H. P., Han, H. S., Hwang, Y., ... & Kim, I. W. (2016). A brief review on relaxor ferroelectrics and selected issues in lead-free relaxors. *Journal of the Korean Physical Society*, 68(12), 1481-1494. [CrossRef]
- [7] Shvartsman, V. V., & Lupascu, D. C. (2012). Lead-free relaxor ferroelectrics. *Journal of the American Ceramic Society*, 95(1), 1-26. [CrossRef]
- [8] Swain, S., Kar, S. K., & Kumar, P. (2015). Dielectric, optical, piezoelectric and ferroelectric studies of NBT-BT ceramics near MPB. *Ceramics International*, 41(9), 10710-10717. [CrossRef]
- [9] Isupov, V. A., Smolenskii, G. A., Agranovskaya, A. I., & Krainik, N. N. (1961). New ferroelectrics of complex composition. *Sov. Phys.-Solid State*, 2, 2651-2654.
- [10] Smolenskii, G. A., Isupov, V. A., Agranovskaya, A. I., & Popov, S. N. (1961). Ferroelectrics with diffuse phase transitions. *Soviet Physics-Solid State*, 2(11), 2584-2594.
- [11] Panda, P. K. (2009). Environmental friendly lead-free piezoelectric materials. *Journal of materials science*, 44(19), 5049-5062. [CrossRef]
- [12] Ranjan, R. (2020). Na 1/2 Bi 1/2 TiO<sub>3</sub>-based lead-free piezoceramics. *Current Science*, 118(10), 1507-1519. <https://www.jstor.org/stable/27138777>
- [13] Liu, G., Hu, L., Wang, Y., Wang, Z., Yu, L., Lv, J., ... & Yan, Y. (2020). Investigation of electrical and electric energy storage properties of La-doped Na<sub>0.3</sub>Sr<sub>0.4</sub>Bi<sub>0.3</sub>TiO<sub>3</sub> based Pb-free ceramics. *Ceramics International*, 46(11), 19375-19384. [CrossRef]
- [14] Ullah, A., Yao, Z., Liu, H., Hao, H., Manan, A., Ullah, A., ... & Alresheedi, F. (2021). Improved energy storage properties of La<sub>0.33</sub>NbO<sub>3</sub> modified 0.94 Bi<sub>0.5</sub>Na<sub>0.5</sub>TiO<sub>3</sub>-0.06 BaTiO<sub>3</sub> ceramic system. *Applied Physics A*, 127(2), 150. [CrossRef]
- [15] Sasaki, A., Chiba, T., Mamiya, Y., & Otsuki, E. (1999). Dielectric and piezoelectric properties of (Bi<sub>0.5</sub>Na<sub>0.5</sub>)TiO<sub>3</sub>-(Bi<sub>0.5</sub>K<sub>0.5</sub>)TiO<sub>3</sub> systems. *Japanese Journal of Applied Physics*, 38(9S), 5564. [CrossRef]
- [16] Shannon, R. D. (1976). Revised effective ionic radii and systematic studies of interatomic distances in halides and chalcogenides. *Foundations of Crystallography*, 32(5), 751-767. [CrossRef]
- [17] Zhou, C., Liu, X., Li, W., & Yuan, C. (2009). Structure and piezoelectric properties of Bi<sub>0.5</sub>Na<sub>0.5</sub>TiO<sub>3</sub>-Bi<sub>0.5</sub>K<sub>0.5</sub>TiO<sub>3</sub>-BiFeO<sub>3</sub> lead-free piezoelectric ceramics. *Materials Chemistry and Physics*, 114(2-3), 832-836. [CrossRef]
- [18] Aksel, E., & Jones, J. L. (2010). Advances in lead-free piezoelectric materials for sensors and actuators. *Sensors*, 10(3), 1935-1954. [CrossRef]
- Afzal Shah** is working as a Professor in the department of Chemical Sciences, University of Science & Technology Bannu, Khyber Pakhtunkhwa, Pakistan. (Email: dr.afzalshah@ustb.edu.pk)
- Shakeela Naz** received the MS degree in Chemistry from the department of Chemical Sciences, University of Science & Technology Bannu, Khyber Pakhtunkhwa, Pakistan and is currently doing PhD from the same department. (Email: Naz123@gmail.com)
- Shah Faisal** received the MS degree in Chemistry from the department of Chemical Sciences, University of Science & Technology Bannu, Khyber Pakhtunkhwa, Pakistan in 2024. (Email: sf8443@gmail.com)
- Qaisar Iqbal** received the B.S. degree in Physics from the department of Physics and Materials Science, University of Science & Technology Bannu, Khyber Pakhtunkhwa, Pakistan in 2025. His research focus on processing of dielectric materials for telecommunication as well as energy storage capacitors. (Email: qaisar11223301@gmail.com)
- Sher Abdullah** received the B.S. degree in Physics from the department of Physics and Materials Science, University of Science & Technology Bannu, Khyber Pakhtunkhwa, Pakistan in 2024. His research focus on processing of dielectric materials for telecommunication as well as energy storage capacitors. (Email: sherabdullah2023@gmail.com)
- Abdul Manan** received the PhD. degree in Physics, from the department of Physics, University of Peshawar Pakistan in 2011. He did his Postdoctorate from School of Materials Science and Engineering, Wuhan University Technology, China in 2017 as well as from the Materials Research Institute, the Pennsylvania State University, USA in 2023. His research focus on the designing of dielectric materials for resonators, energy storage capacitors applications etc. He is the author of more than 100 research articles. He is currently working as an Associate Professor at the Department of Physics and Materials Science, University of Science & Technology Bannu, Pakistan. (Email: drmanan82@ustb.edu.pk, drmanan82@yahoo.com)